



RDC QUALITY REP.
EDUARDO A, LOPEZ

JOB NO: F-0517-0194

CUSTOMER : TESCORP

DATE : 6/24/17


EQUIPMENT : SKID FRAME & PARTS

BLAST/SURFACE PREPARATION

REQUIREMENT : SSPC-SP6

PROFILE : COMMERCIAL BLAST

SURFACE PREP : JOSE SEVERINO

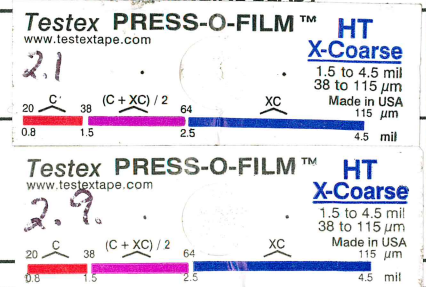

DATE : 6/24/17

BLAST MATERIAL SAND -20/40

CONDITION AT START TIME

MATERIAL/ EQUIPMENT	TIME	DATE	AMB TEMP *F	DEW PT *F	MAX REL. HUM %	SURFACE TEMP *F
SANDBLASTING	9:00 AM	6/24/17	84.6	63.4	53..3	87.8
PRIMER	2:00 PM	6/24/17	89.9	59.7	32.8	94.6
TOP COAT	1:00 PM	6/25/17	91.8	52.6	26.4	90.1

COATING INSPECTION/RECORDING IN D.F.T. MILS

COATING INCLUDING BATCH NUMBER	REQ'D MILS	MILS READING	INSPECTION BY:	PAINTER NAME
MACROPOXY 646	4 - 6 MILS	4.54	EAL	EDUARDO A LOPEZ
PART A = XM1327XG		4.78		
PART B = XM1447GH		6.31		
		4.56 AVG		
HI SOLID POLYURETHAN (DESERT TAN)	2 - 3 MILS	5.32	EAL	EDUARDO A LOPEZ
PART S= XM1425WJ		7.78		
PART T= MQ1147TY		9.02		
TOTAL	6 - 9 MILS	9.02 AVG		



RDC QUALITY REP.
EDUARDO A, LOPEZ

JOB NO: F-0517-0195

CUSTOMER : TESCORP

DATE : 7/14/17

EQUIPMENT : SKID FRAME & PARTS

BLAST/SURFACE PREPARATION


REQUIREMENT : SSPC-SP6

PROFILE : COMERCIAL BLAST

SURFACE PREP : EDUARDO A LOPEZ

DATE : 7/14/17

BLAST MATERIAL SAND -20/40

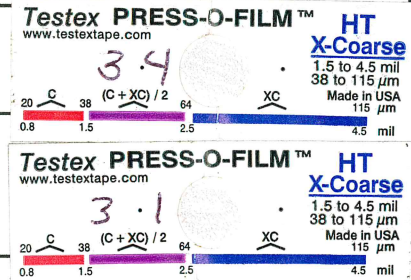

CONDITION AT START TIME

MATERIAL/ EQUIPMENT	TIME	DATE	AMB TEMP *F	DEW PT *F	MAX REL. HUM %	SURFACE TEMP *F
SANDBLASTING	8:00 AM	7/14/17	80.2	65.3	63.6	80
PRIMER	12:45 PM	7/14/17	84.1	78.6	79.8	83.2
TOP COAT	9:30 AM	7/16/17	87.6	66.9	70.7	90.4

COATING INSPECTION/RECORDING IN D.F.T. MILS

COATING INCLUDING BATCH NUMBER	REQ'D MILS	MILS READING	INSPECTION BY:	PAINTER NAME
MACROPOXY 646	4 - 6 MILS	5.76	EAL	EDUARDO A LOPEZ
PART A = XM1327XG		4.98		
PART B = XM1447GH		6.34		
		AVG 5.45		
HI SOLID POLYURETHAN (DESERT TAN)	2 - 3 MILS	11.2	EAL	EDUARDO A LOPEZ
PART S= XM1425WJ		8.37		
PART T= MQ1147TY		10.24		
		AVG 9.98		
TOTAL	6 - 9 MILS	9.98		



RDC QUALITY REP.
EDUARDO A, LOPEZ

JOB NO: F-0517-0197

CUSTOMER : TESCORP

DATE : 10/2/17


EQUIPMENT : SKID FRAME & PARTS

BLAST/SURFACE PREPARATION

REQUIREMENT : SSPC-SP6


PROFILE : COMMERCIAL BLAST

SURFACE PREP : JOSE SEVERINO

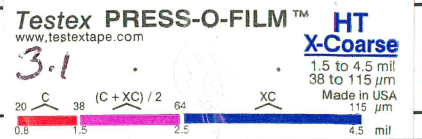

DATE : 10/2/17

BLAST MATERIAL SAND -20/40

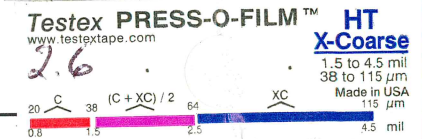

CONDITION AT START TIME

MATERIAL/ EQUIPMENT	TIME	DATE	AMB TEMP *F	DEW PT *F	MAX REL. HUM %	SURFACE TEMP *F
SANDBLASTING	8:45 AM	10/2/17	79.3	73.7	60.8	81.6
PRIMER	3:30 PM	10/2/17	88.5	72.5	58.3	93.1
TOP COAT	9:00 AM	10/3/17	81.8	72.5	72.3	82.6

COATING INSPECTION/RECORDING IN D.F.T. MILS

COATING INCLUDING BATCH NUMBER	REQ'D MILS	MILS READING	INSPECTION BY:	PAINTER NAME
AMERGUARD 370	4 - 6 MILS	5.3	MV	EUSEVIO LOPEZ
RESIN = 9720256651		4.7		
CURE = 9609912147		4.5		
		AVG 4.99		
AMERSHIELD 450	2 - 3 MILS	8.6	MV	MIGUEL NAVARRO
RESIN = 972528084		9.4		
CURE = WB704306		7.4		
		6.6		
TOTAL	6 - 9 MILS	AVG 7.23		

